Development of the latest generation of CORC® wires and their implementation into high-field dipole magnets

Danko van der Laan
Advanced Conductor Technologies & University of Colorado, Boulder, Colorado, USA

Sven Dönges, Daniel Kwiatkowski, Kyle Radcliff & Griffin Bradford
Advanced Conductor Technologies, Boulder, Colorado, USA

Dima Abraimov
Applied Superconductivity Center, National High Magnetic Field Laboratory, Tallahassee, Florida, U.S.A.

Xiaorong Wang, Yufan Yan, Lucas Brouwer, José Luis Rudeiros Fernandez, Hugh Higley & Soren Prestemon
Lawrence Berkeley National Laboratory, Berkeley, California, U.S.A.

This work was in part supported by the US Department of Energy under agreement numbers DE-SC0014009, DE-SC0015775, DE-SC0024159, DE-SC0024760 and DE-SC0025836.

CORC® wire overview

Future 20 T accelerator magnets require flexible high I_c and high J_e CORC® conductors

- Operating current > 10 kA, engineering current density (J_e) > 600 A/mm^2
- Bending to 20 mm radius without significant degradation



Route to achieve required performance

- Use of high-performance REBCO tapes of 2 mm width
- Minimize the CORC® wire core size by using REBCO tapes with thin substrates

Effect of substrate thickness on allowable core size



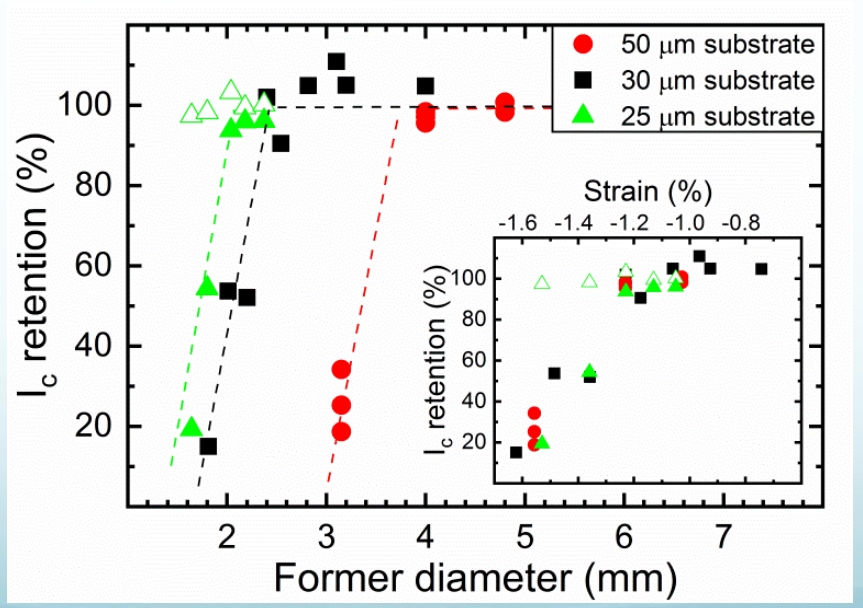

Minimum core diameter

- 4 mm for 50 μm substrate
- 3.2 mm for 38 μm substrate
- 2.4 mm for 30 μm substrate
- 2.0 mm for 25 μm substrate

Typical CORC® wire (3.6 - 3.7 mm thick)

- Wound from tapes with 30 μm substrate
- Uses a 2.55 mm core
- Contains 30 tapes

Status of stand-alone CCT magnets based on CORC® wires

CCT magnet development based on CORC® wires

Achieve a dipole field of 20 T over several stages

1. Developing and demonstrating the CORC®-based CCT magnet technology
2. Improve the bending performance of CORC® wires to minimize winding degradation
3. Develop high-J_e and high I_c CORC® wires that allow operation at **10 kA at 20 T**

2017: Demonstration of 1.2 T (CCT-C1)

- 2-Layer coil, 40 turns per layer
- Low-J_e, 16-tape CORC® wire
- Generated 1.2 T at 4.5 kA

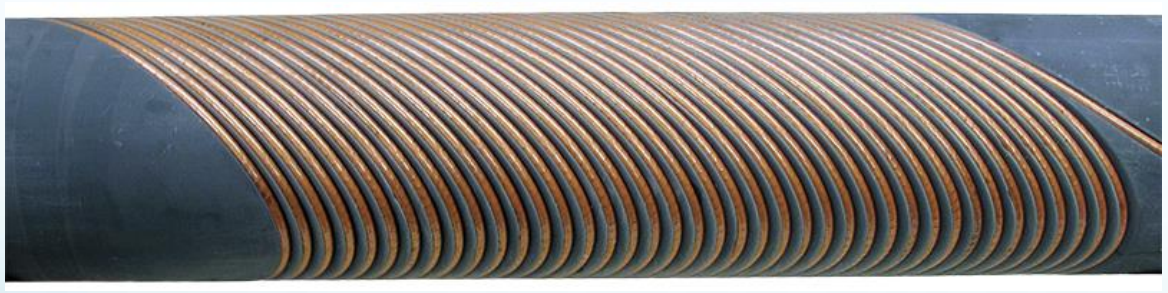

CORC® CCT-C1

A 1.2-T canted cos ϑ dipole magnet using high-temperature superconducting CORC® wires, X. Wang, et al., *Supercond. Sci. Technol.* **32**, 075002 (2019)

2020: Demonstration of 2.9 T (CCT-C2)

- 4-Layer coil, 40 turns per layer, **30 mm radius at poles**
- Medium-J_e, 30-tape CORC® wire
- Generated 2.9 T at 6.5 kA



CORC® CCT-C2

Development and performance of a 2.9 Tesla dipole magnet using high-temperature superconducting CORC® wires, X. Wang, et al., *Supercond. Sci. Technol.* **34**, 015012 (2021)

Development for magnet CCT-C3 to generate a 5 T dipole field

How to reach 5 T in CCT-C3?

- Magnet containing 6 layers with 40 turns each, requiring 145 meters of CORC® wire
- Keeping the 30 mm minimum bending radius at poles
- High-J_e 30-tape CORC® wires using SuperPower's HM tapes

Performance of SuperPower SCS2030-HM tape 2021 - 2022

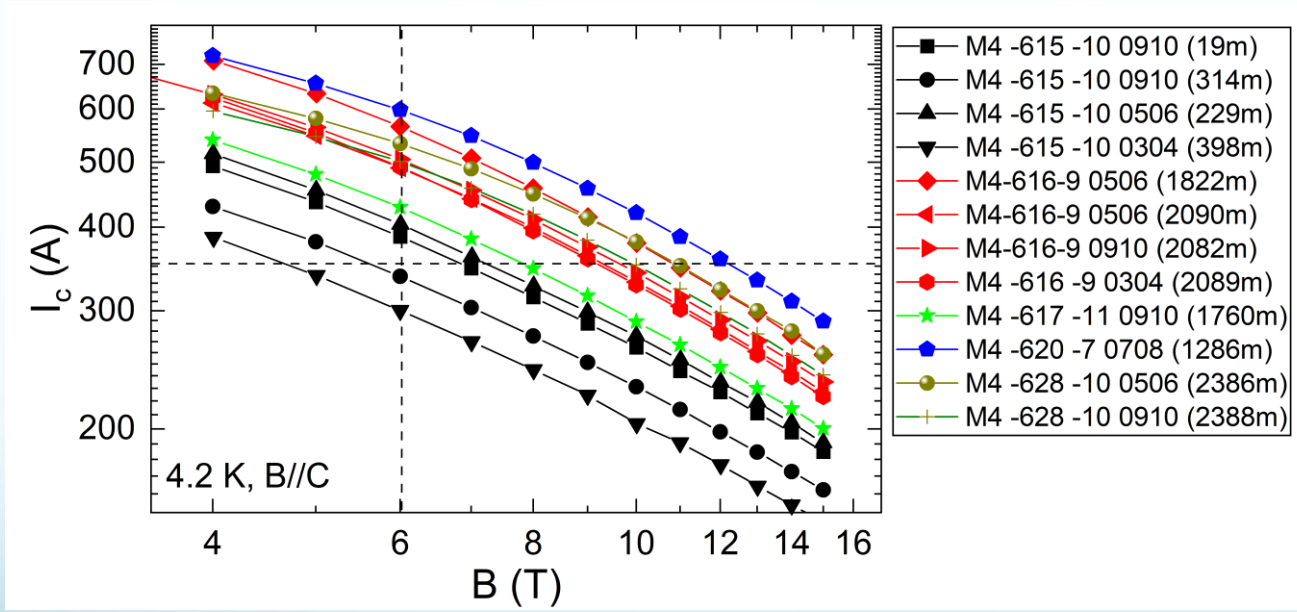

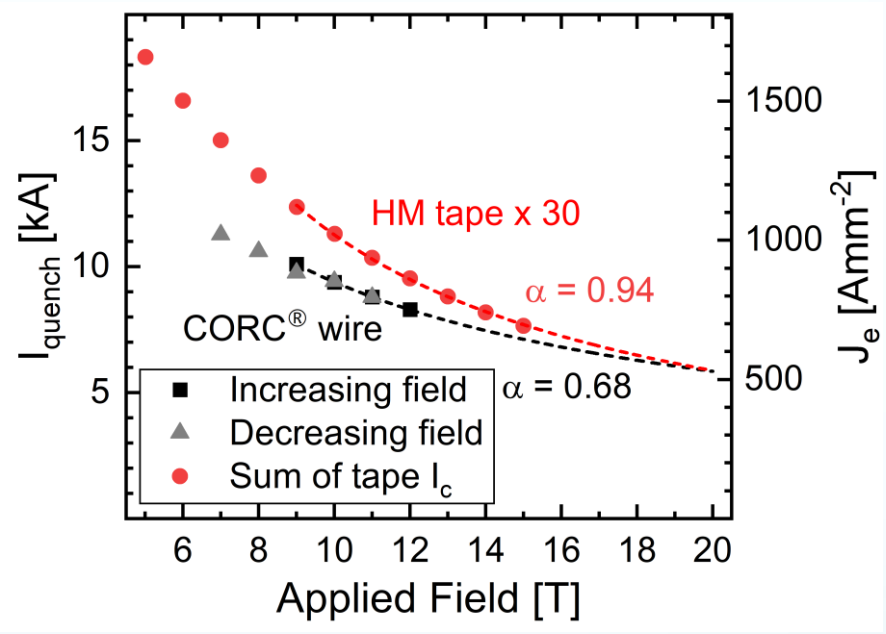

CORC® wire (SuperPower HM tapes)

- Tested at 31.5 mm radius hairpin
- **Record J_e(20 T) of 530 A/mm^2 at I_c of 5 kA**
- 87 % of tape performance at 12 T

Danko van der Laan, Jeremy Weiss, Kyle Radcliff and Dmytro Abraimov, *Supercond. Sci. Technol.* **37** 115007 (2024)

Dipole magnet CCT-C3 generates 5.99 T dipole field!

Magnet CCT-C3 exceeded its target of 5 T dipole field

- **Dipole field of 5.99 T achieved at 6.795 kA**
- Much lower CORC® wire bending degradation than 30 % as assumed in the original magnet design
- Inner layer (Layer 1) transition started and reached about 0.1 μV/cm but may have room to reach a dipole field of 6.2 – 6.3 T!

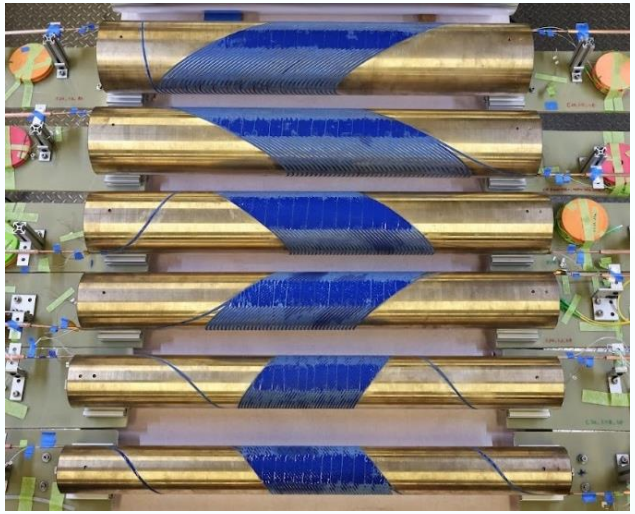

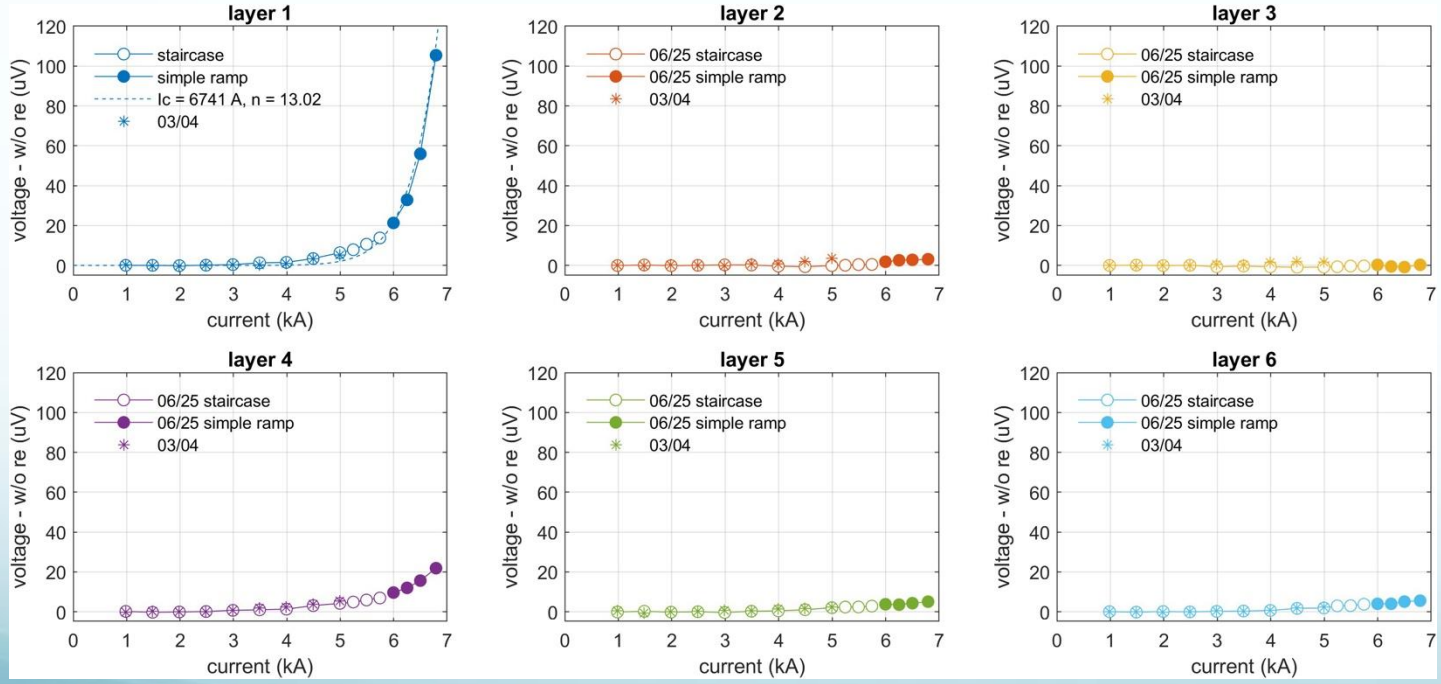

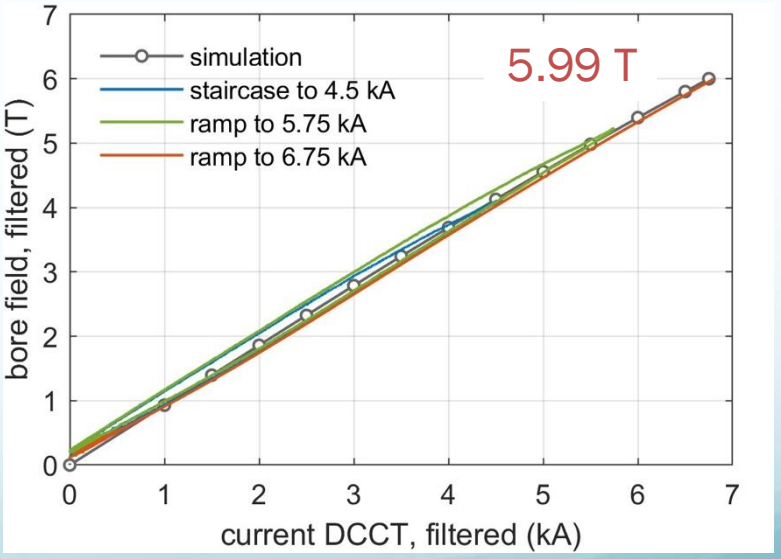

Dmytro Abraimov, et al., *Phys. Rev. Accelerators and Beams.* **29** 083902 (2026)

Development of the next CCT magnet

Development of magnet CCT-C4 generating 10 T dipole field

CCT-C4 magnet layout

- Target dipole field 10 T
- Magnet bore 65 mm, O.D. 225 mm
- Bending radius at pole 30 mm
- 8 layers
- Transfer function 0.898 T/kA (no iron)
- Transfer function 1.053 T/kA (with iron)
- Operating current 9.6 kA to generate 10 T (with iron)

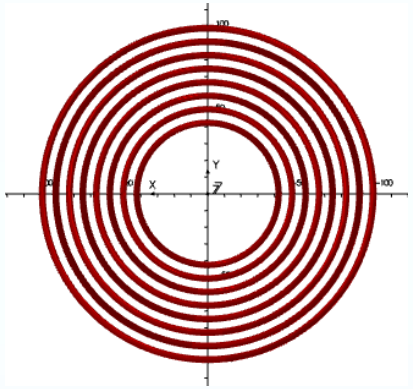

CORC® wire performance (see later slide)

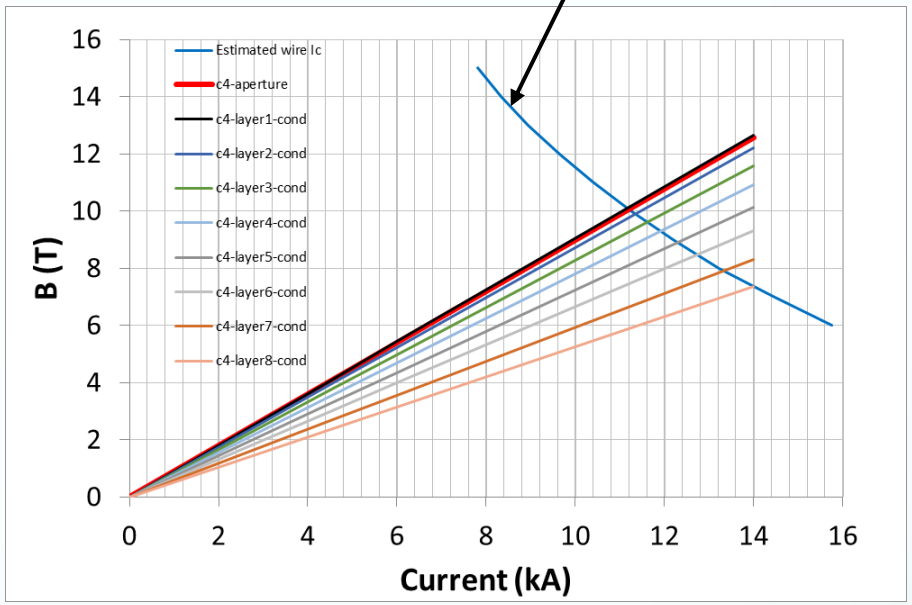

Conductor performance requirements a major step above CCT-C3

1. **CORC® wire capable of operating at 10 kA at 10 T instead of 5.66 kA at 5 T for CCT-C3**
2. **Operation at 100 kN/m instead of about 40 kN/m for CCT-C3**

CORC® wire requirements for a 10 kA, 10 T CCT dipole

Required electrical conductor performance for CCT-C4

- Operating current of 10 kA at 10 T requires I_c of at least 13 kA
- Best SuperPower HM CORC® wire has I_c(10 T) of 9.2 kA
- **Over 40 % increase in tape performance needed**

CCT-C3 CORC® wire (SuperPower HM tapes)

- CORC® performance 87 % of tape
- Tested at 99.5 kN/m transverse load
- **Expected I_c at 10 T of 9.2 kA**

Mechanical resilience of CORC® wire

- **Transverse load on CORC® wire of 100 kN/m in CCT-C4**
- CCT-C3 operated at 40 kN/m transverse compression
- SuperPower HM based CORC® wire was tested at 99.5 kN/m without degradation, which may be near its critical limit

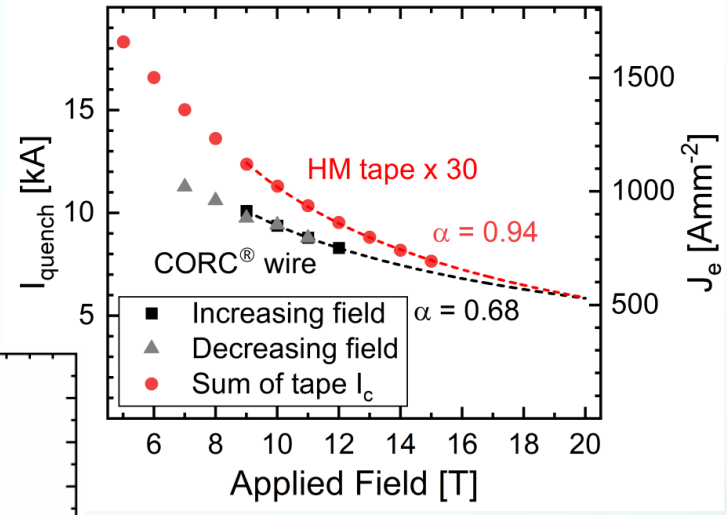

Critical transverse load of CORC® conductors

- Tested using two flat anvils (not Lorenz force driven)
- Depends on the CORC® core size:
  - 2.55 mm core: around 100 kN/m
  - 3.2 mm core: around 200 kN/m

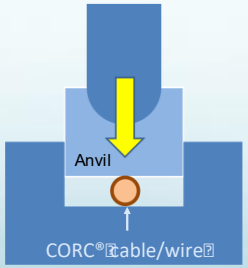

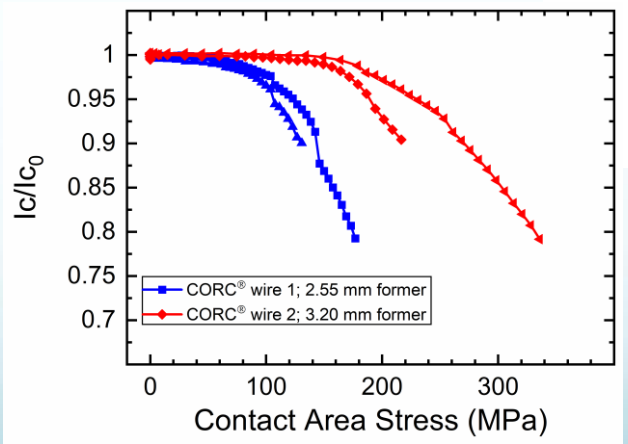

Danko van der Laan, Dustin Mc Rae & Jeremy Weiss, *Supercond. Sci. Technol.* **32** 015002 (2019)

Developing a 10 kA (10 T) CORC® wire for CCT-C4

Availability of compatible tapes for use in CORC® wires: substrate thickness of less than 35 μm

2020: SuperPower HM

- Until recently the highest in-field performance
- 30 μm thick substrate
- Limited availability

2023: Shanghai Superconductor Technologies (SST)

- 30 μm thick substrates
- About 2/3 of SuperPower HM performance

2025: High-*I* Shanghai Superconductor Technologies

- **23 μm thick substrates**
- Higher J_c and thicker REBCO film
- Performance comparable with SuperPower HM

2026: Fujikura FASC

- 35 μm thick substrates
- **Performance double that of SuperPower HM**

2 mm wide tape performance at 4.2 K

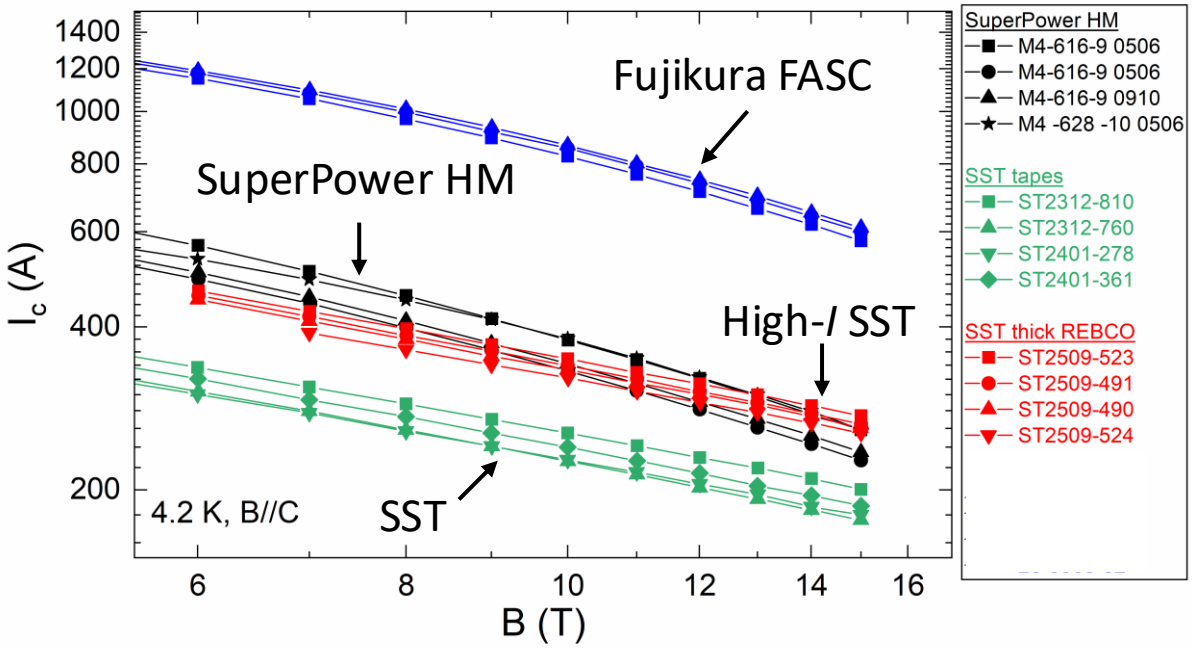

In-field performance of CORC® wires: High-*I* SST tapes

High-*I* SST CORC® wire layout

- Tapes with 23 μm substrate
- **CORC® wire core 2.34 mm**
- 34 tapes, O.D. 3.9 mm
- Expected transverse load limit <100 kN/m

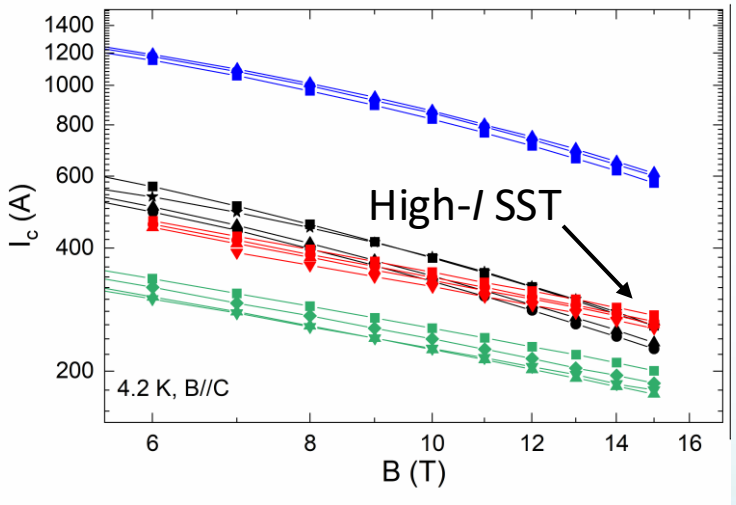

No reinforcement

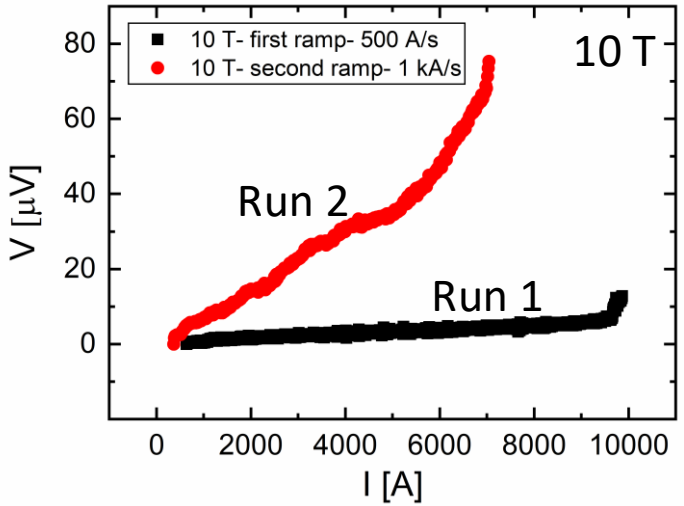

Solder coated tapes

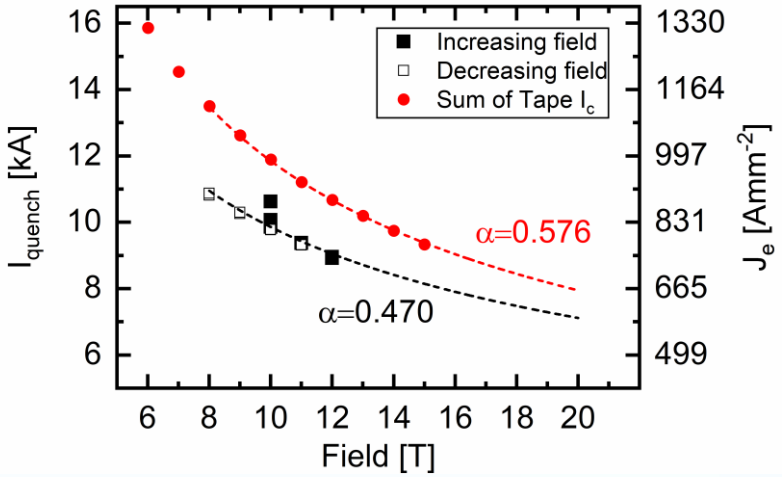

CORC® wire (no reinforcement)

- Quenches at 10 T:
  - 1: 9,875 A
  - 2: 6,900 A
- Degradation of 30 % at 98.8 kN/m

CORC® wire with solder coated tapes

- About 7 % degradation after initial 4 runs, after which it stabilized
- Final CORC® performance 87 % of tape
- **Peak transverse load: 107.4 kN/m at 12 T**
- **I_c at 10 T of 9,800 A**

Transverse load limit based on CORC® core size can be extended by additional CORC® wire reinforcement

In-field performance of CORC® wires: Fujikura FASC

CORC® wire layout

- Tapes with 35 μm substrate
- **CORC® wire core 3.05 mm**
- 24 tapes, O.D. 4.2 mm
- Expected transverse load limit somewhere between 100 and 200 kN/m
- **Theoretical I_c at 10 T of 17.5 kA** (175 kN/m)
- Theoretical I_c at 20 T of 8.7 kA (174 kN/m)

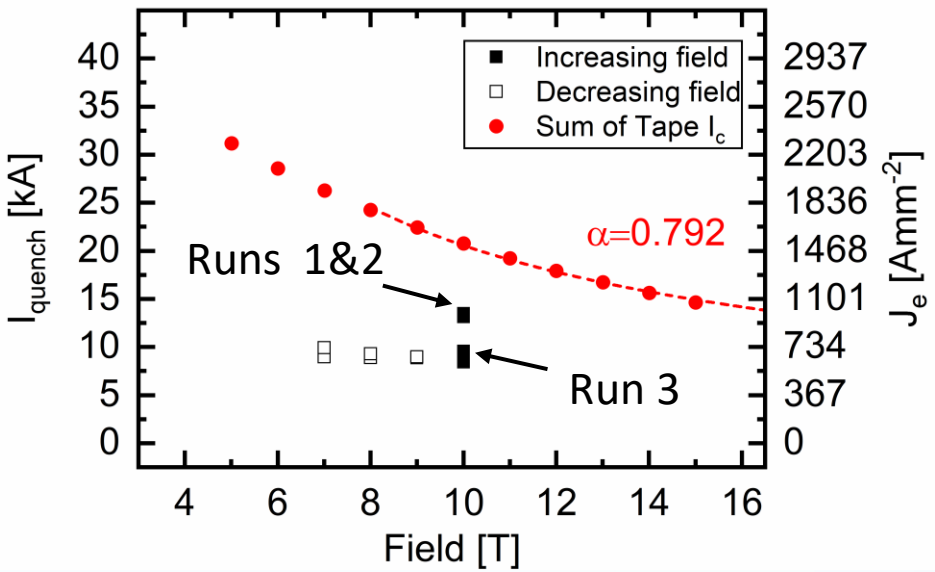

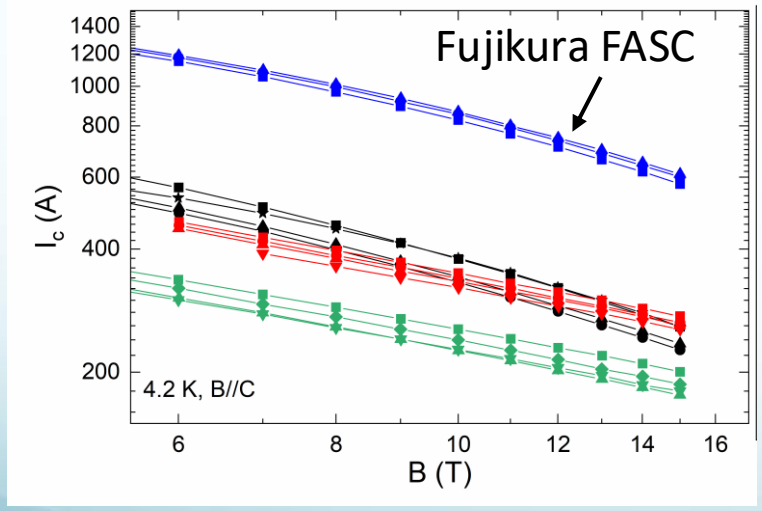

CORC® wire performance

Quenches at 10 T:
1: 13,135 A (131.3 kN/m)
2: **13,489 A (134.9 kN/m)**
3: 8,700 A, …..
21: 8,659 A

Impact

- CORC® wire is not current limited, but stress limited
- Additional reinforcement (larger core, or solder coated tapes) may increase the transverse load limit towards 175 kN/m corresponding to the electrical CORC® wire limit

CCT-C4 can be wound from CORC® wire based on Fujikura FASC tapes without additional support

Inserts for LYS/HTS hybrid accelerator magnets based on CORC® wires

Elliptical CCT magnets wound from CORC® wires at 20 mm radius

CCT magnets with elliptical aperture

- Allow for smaller inserts than circular CCTs
- Allow ellipticity as additional design parameter
- Have a higher transfer function (T/kA) at smaller major radius than circular CCTs

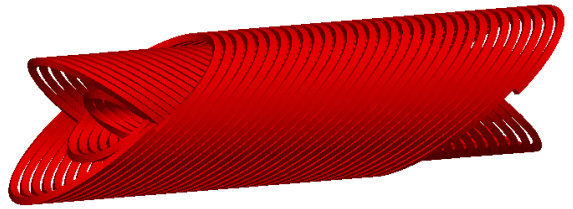



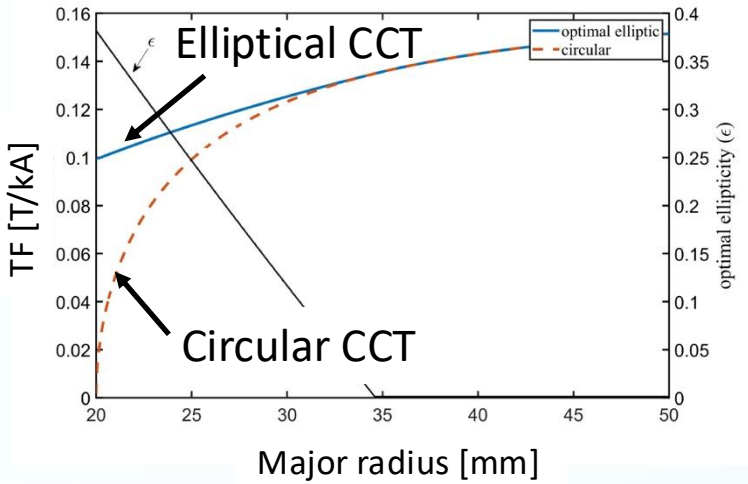

Concept verification at 20 mm CORC® bend radius

5 T (stand-alone), 3 T (in 10 T LTS outsert)

TABLE II
SUMMARY TABLE FOR THE HTS INSERT MAGNET DESIGN

parameter	value	unit
major aperture	36.3	mm
minor aperture	22.0	mm
min. bending radii	20/21/20/23	mm
wire piece lengths	4.0/5.9/11.3/13.7	m
total wire length	34.9	m
physical length	420	mm
Short sample: standalone (4.2 K)		
I_c	11.0	kA
B_1	4.88	T
conductor ⊥ field	5.10	T
magnetic length	241.4	mm
Short sample: in 10 T background (4.2 K)		
I_c (HTS)	6.58	kA
B_1 (HTS)	2.92	T
B_1 (total)	12.92	T
conductor ⊥ field (HTS)	13.05	T

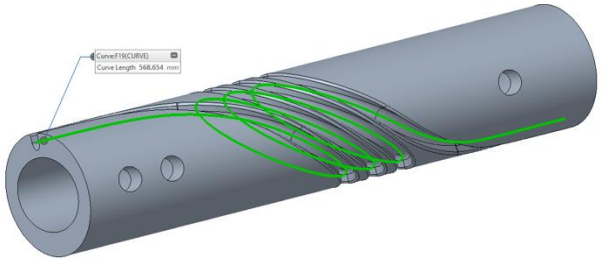

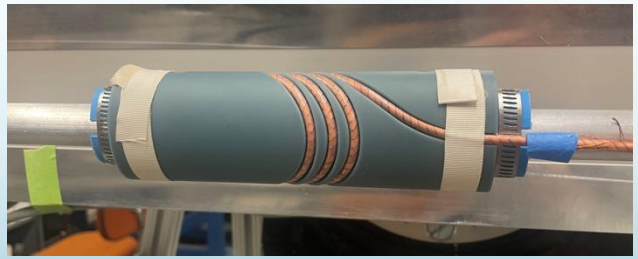

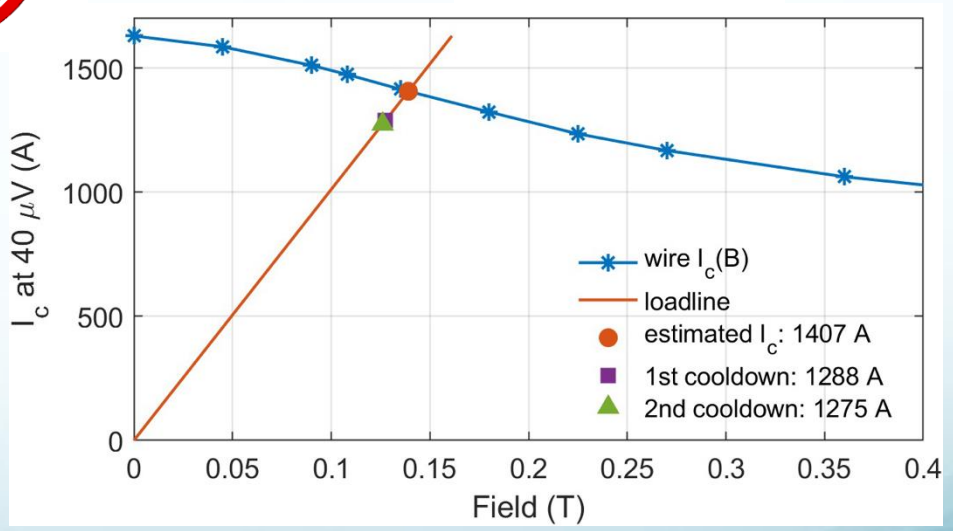

L. Brouwer, Y. Yan, X. Wang, J.F. Croteau, P. Ferracin, J.L Rudeiros Fernandez, and A. Saravanan, *IEEE Trans. Appl. Sup.* 36, 4600107(2026)

Uni-layer dipole magnets wound from CORC® wires at 20 mm radius

Uni-layer magnets have certain benefits

- More efficient use of conductor over others
- Allow for small aperture while limiting conductor bending radius
- Much higher transfer function than Cosine Theta and CCT magnets

Concept verification

- 20 mm bend radius
- Performance 90 % after winding, not taking field into account

Uni-layer magnet program at LBNL

- 5.5 T at 9.8 kA stand-alone
- 12.1 T at 6.5 kA within 8.5 T LTS outsert

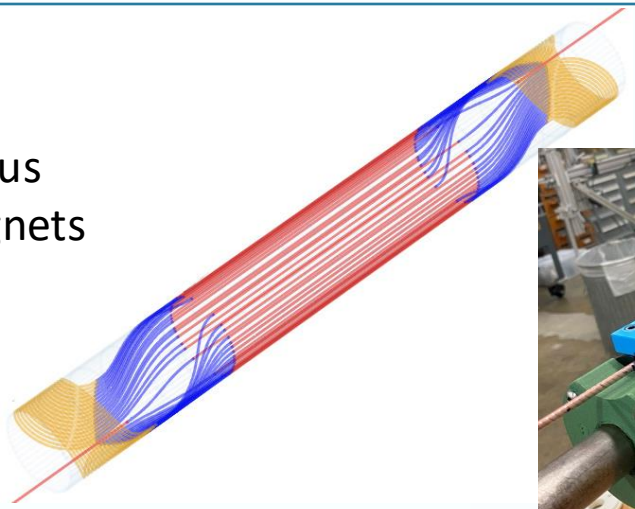

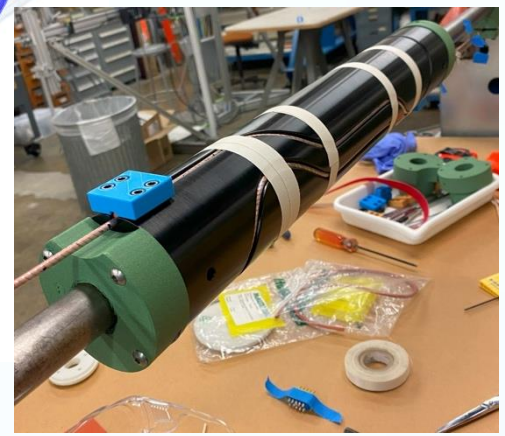

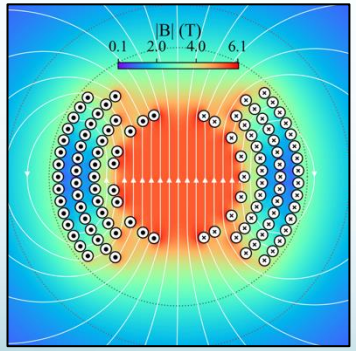

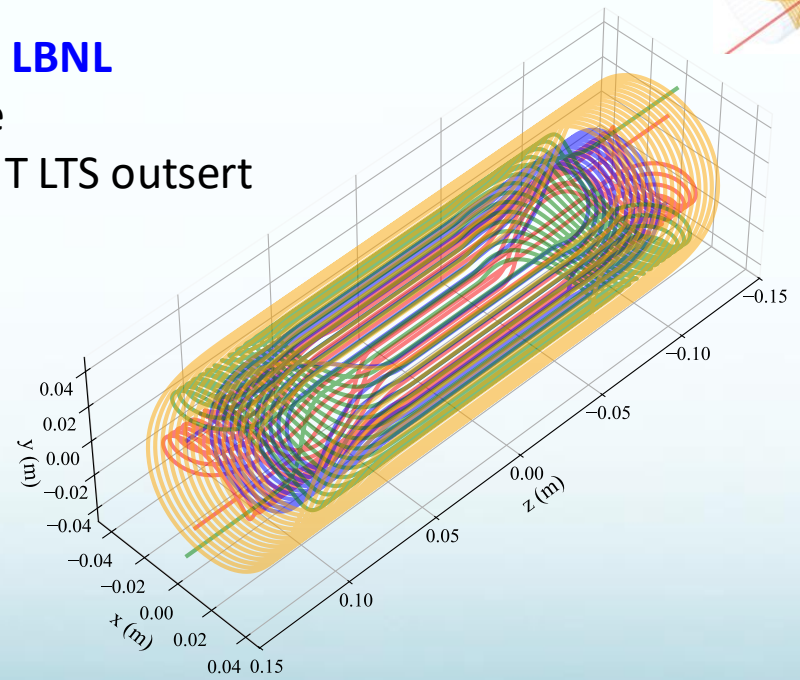

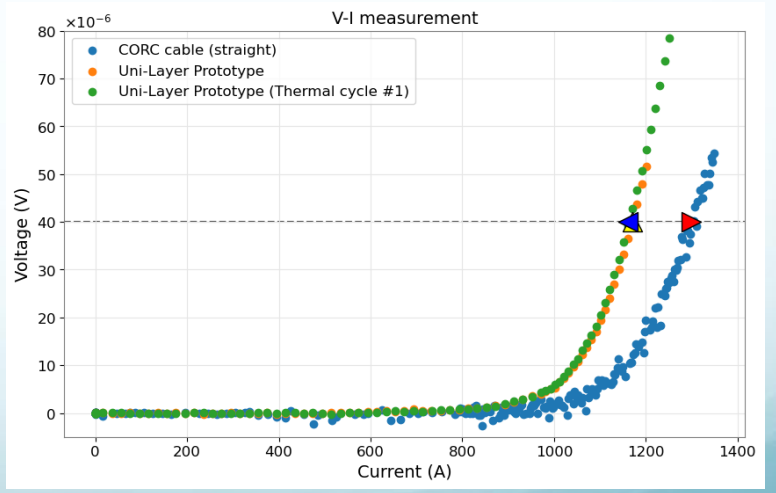

J.L Rudeiros Fernandez and P. Ferracin, *Superconduct. Sci. Technol.* **36** 055003 (2023)

Advanced Conductor Technologies
www.advancedconductor.com

NATIONAL HIGH MAGNETIC FIELD LABORATORY
BERKELEY LAB

Summary

Development of dipole magnets based on CORC® wires

- Canted-cosine-theta magnets have demonstrated 1.2 T, 2.9 T and 5.99 T dipole fields
- The improved bending performance of CORC® wires resulted in a dipole field of 5.99 T in the latest CCT magnet, overshooting its 5 T target by 20 %
- Improved bending flexibility of CORC® wires now allows compact and more efficient CCT magnets with minimum bending radius of 20 mm
- Magnet CCT-C4, generating a dipole field of 10 T at a current of 10 kA is planned

Development CORC® wires for CCT-C4 and beyond

- The electrical performance of CORC® wires can only be achieved with Fujikura FASC tapes, which have 50 % higher in-field performance than Superpower HM tapes used in CCT-C3
- CORC® wires based on Fujikura FASC tapes are stress limited under transverse compression at about 75 % of their theoretical electrical limit
- CORC® wires based on Fujikura FASC tapes are compatible with the transverse compressive load of 100 kN/m in CCT-C4
- An optimized CORC® wire design is required to allow operation at transverse loads of 200 kN/m in a 20 T dipole magnet operating at 10 kA